

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

SPONSOR: **ARTIZIN™**
Garland, TX

Sound Absorption
RAL™-A22-484

CONDUCTED: 2022-11-04

Page 1 of 9

ON: ArtFelt™ 9mm Acoustic Panel

TEST METHODOLOGY

Riverbank Acoustical Laboratories™ is accredited by the U.S. Department of Commerce, National Institute of Standards and Technology (NIST) under the National Voluntary Laboratory Accreditation Program (NVLAP) as an ISO 17025:2017 Laboratory (NVLAP Lab Code: 100227-0) and for this test procedure. The test reported in this document conformed explicitly with ASTM C423-22: "Standard Test Method for Sound Absorption and Sound Absorption Coefficients by the Reverberation Room Method." The specimen mounting was performed according to ASTM E795-16: "Standard Practices for Mounting Test Specimens During Sound Absorption Tests." A description of the measurement procedure and room specifications are available upon request. The results presented in this report apply to the sample as received from the test sponsor.

INFORMATION PROVIDED BY SPONSOR

The test specimen was designated by the sponsor as ArtFelt™ 9mm Acoustic Panel. The following nominal product information was provided by the sponsor prior to testing. The accuracy of such sponsor-provided information can affect the validity of the test results.

Product Under Test

Product Name: ArtFelt™ 9mm Acoustic Panel
Core Material: PET
Thickness: 9mm
Dimensions: 48"x96"
Manufacturer: ARTIZIN™

SPECIMEN MEASUREMENTS & TEST CONDITIONS

Through a full external visual inspection performed on the test specimen, Riverbank personnel verified the following information:

Test Specimen

Dimensions: 2 panels @ 1219 mm (48 in.) by 2438 mm (96 in.)
Thickness: 9.4 mm (0.37 in.)
Overall Weight: 11.79 kg (26 lbs)
Mass per Unit Volume: 211 kg/m³ (13.2 lbs/ft³)

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

ARTIZIN™
2022-11-04

RAL™-A22-484
Page 2 of 9

Overall Specimen Properties

Size: 2.44 m (96.0 in) wide by 2.44 m (96.0 in) long
Thickness: 0.01 m (0.37 in)
Weight: 11.79 kg (26.0 lbs)
Mass per Unit Area: 1.98 kg/m² (0.41 lbs/ft²)
Calculation Area: 5.946 m² (64. ft²)

Test Environment

Room Volume: 291.98 m³
Temperature: 21.3 °C ± 0.1 °C (Requirement: ≥ 10 °C and ≤ 5 °C change)
Relative Humidity: 58.35 % ± 1.9 % (Requirement: ≥ 40 % and ≤ 5 % change)
Barometric Pressure: 98.4 kPa (Requirement not defined)

MOUNTING METHOD

Type A Mounting: The test specimen was laid directly against the test surface. Perimeter edges were sealed with metal framing and tape.

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

ARTIZIN™
2022-11-04

RAL™-A22-484
Page 3 of 9



Figure 1 – Specimen mounted in test chamber



Figure 2 – Individual specimen panel

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

ARTIZIN™
2022-11-04

RAL™-A22-484
Page 4 of 9

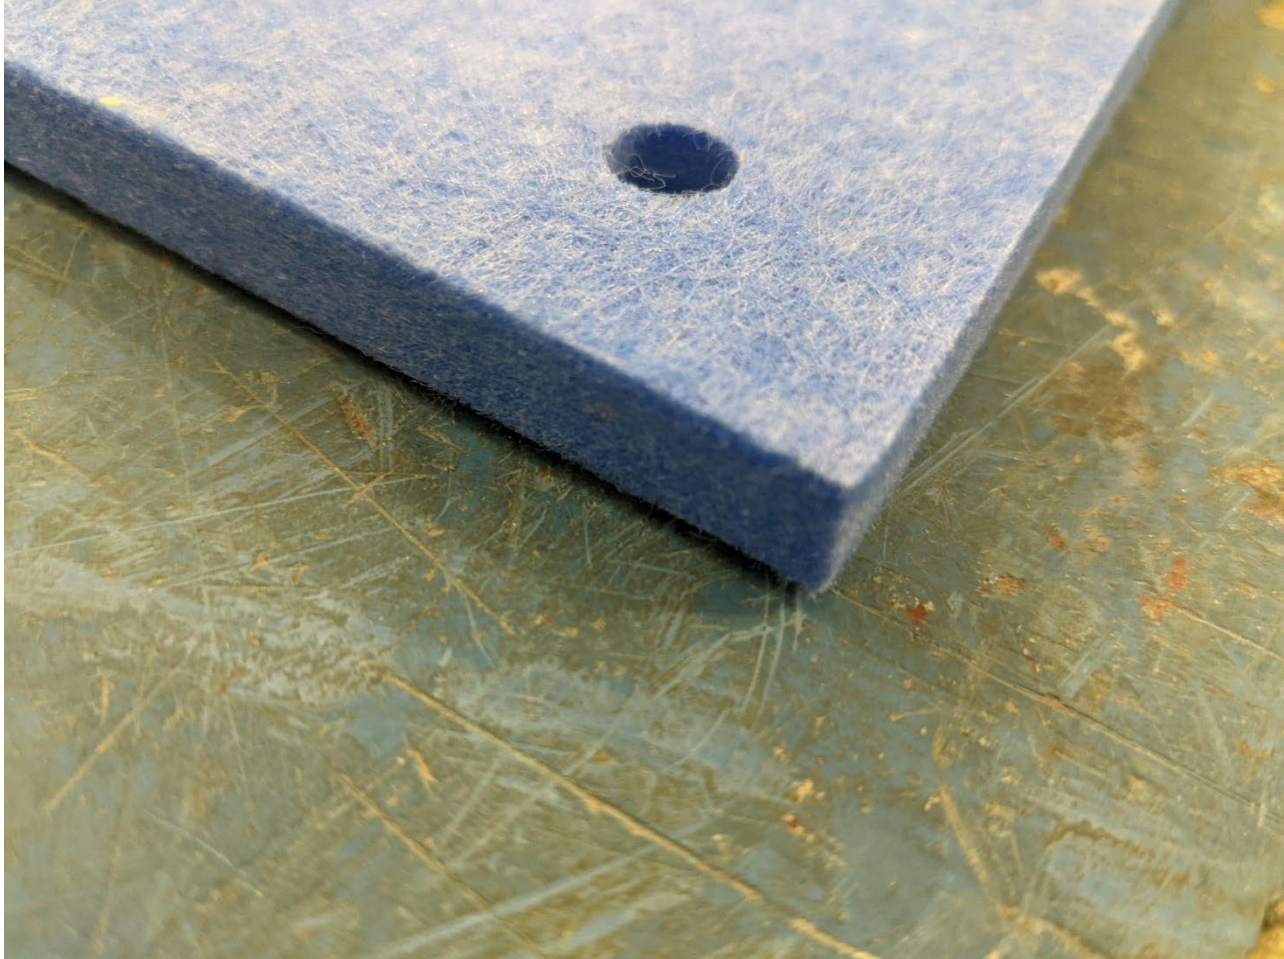


Figure 3 – Detail of specimen material

1512 S BATAVIA AVENUE
 GENEVA, IL 60134
 630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
 WALLACE CLEMENT SABINE

ARTIZIN™
 2022-11-04

RAL™-A22-484
 Page 5 of 9

TEST RESULTS

Specimen total absorption and absorption coefficient are tabulated at the eighteen standard frequencies. A graphic presentation of the data and additional information appear on the following pages.

1/3 Octave Center Frequency (Hz)	Total Absorption (m ²)	Total Absorption (Sabins)	Absorption Coefficient
100	-0.52	-5.59	-0.09
** 125	0.36	3.84	0.06
160	-0.02	-0.24	0.00
200	0.03	0.32	0.00
** 250	0.20	2.15	0.03
315	0.42	4.47	0.07
400	0.44	4.72	0.07
** 500	0.83	8.94	0.14
630	1.09	11.75	0.18
800	1.61	17.28	0.27
** 1000	2.30	24.81	0.39
1250	3.14	33.84	0.53
1600	3.78	40.72	0.64
** 2000	4.24	45.66	0.71
2500	4.76	51.22	0.80
3150	5.39	57.97	0.91
** 4000	5.63	60.64	0.95
5000	6.22	66.99	1.05

SAA = 0.32
NRC = 0.30

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE


ARTIZIN™
2022-11-04

RAL™-A22-484
Page 6 of 9


TEST RESULTS (continued)

The sound absorption average (SAA) is defined in ASTM C423-17 Section 3.1.1 as the arithmetic average of the sound absorption coefficients of a material for the twelve one-third octave bands from 200 Hz through 2500 Hz, inclusive, rounded to the nearest integer multiple of 0.01.

The noise reduction coefficient (NRC) is defined from previous versions of ASTM C423 as the arithmetic average of the sound absorption coefficients at 250 Hz, 500 Hz, 1000 Hz, and 2000 Hz, rounded to the nearest integer multiple of 0.05.

Tested by 
Marc Sciaky
Senior Experimentalist

Report by 
Keith Kimberling
Test Engineer

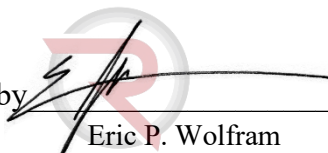Approved by 
Eric P. Wolfram
Laboratory Manager

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report


www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

ARTIZIN™
2022-11-04

RAL™-A22-484
Page 7 of 9

SOUND ABSORPTION REPORT ArtFelt™ 9mm Acoustic Panel

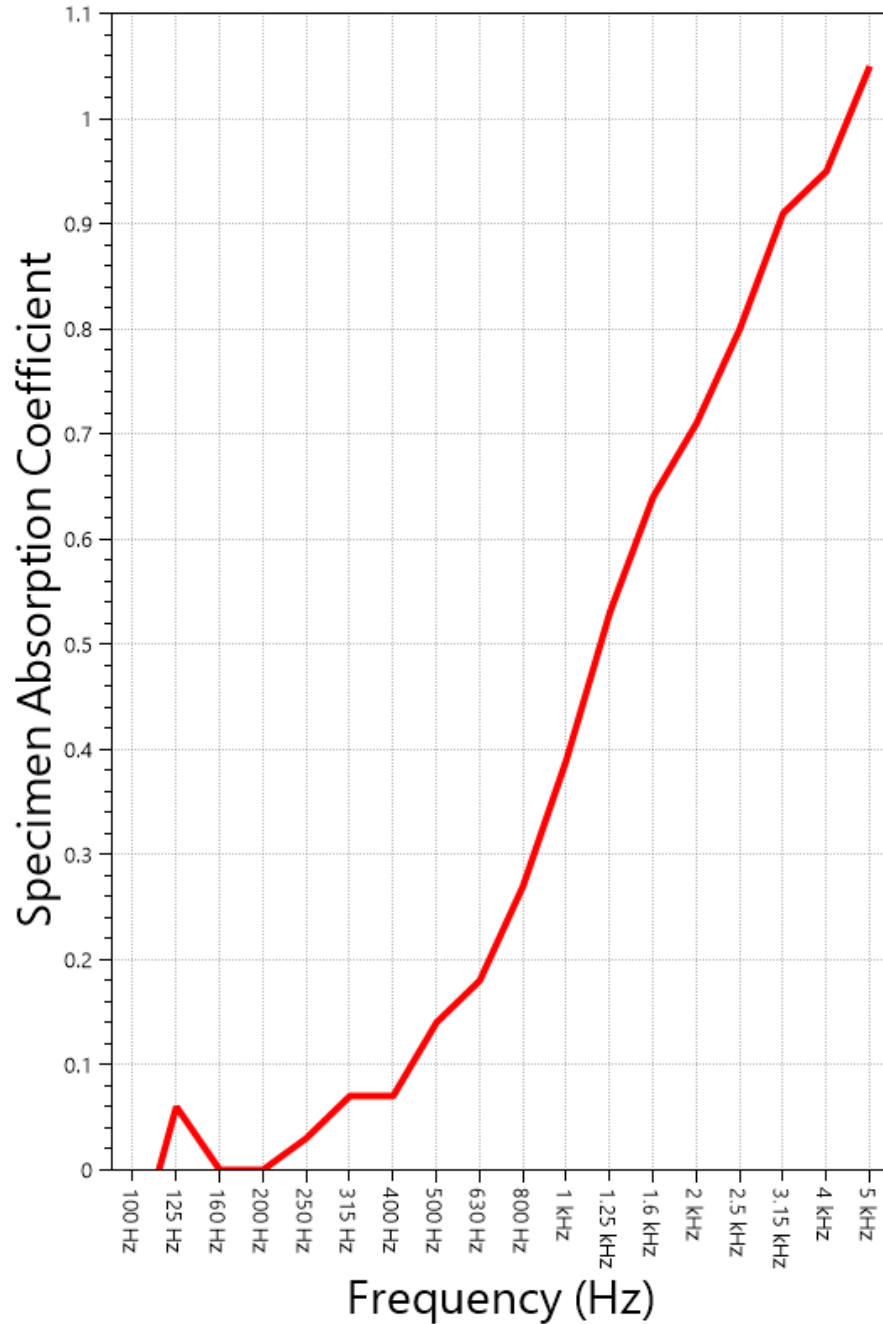

SAA = 0.32

NRC = 0.30



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE
 GENEVA, IL 60134
 630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
 WALLACE CLEMENT SABINE

ARTIZIN™
 2022-11-04

RAL™-A22-484
 Page 8 of 9

APPENDIX A: Extended Frequency Range Data

Specimen: ArtFelt™ 9mm Acoustic Panel (See Full Report)

The following non-accredited data were obtained in accordance with ASTM C423-22, but extend beyond the defined frequency range of 100Hz to 5,000Hz. These unofficial results are representative of the RAL test environment only and intended for research & comparison purposes.

1/3 Octave Band Center Frequency (Hz)	Total Absorption (Sabins)	Absorption Coefficient
31.5	2.10	0.03
40	0.38	0.01
50	-1.13	-0.02
63	-3.15	-0.05
80	-3.76	-0.06
100	-5.59	-0.09
125	3.84	0.06
160	-0.24	0.00
200	0.32	0.00
250	2.15	0.03
315	4.47	0.07
400	4.72	0.07
500	8.94	0.14
630	11.75	0.18
800	17.28	0.27
1000	24.81	0.39
1250	33.84	0.53
1600	40.72	0.64
2000	45.66	0.71
2500	51.22	0.80
3150	57.97	0.91
4000	60.64	0.95
5000	66.99	1.05
6300	69.63	1.09
8000	72.28	1.13
10000	71.81	1.12
12500	74.17	1.16



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

1512 S BATAVIA AVENUE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

ARTIZIN™
2022-11-04

RAL™-A22-484
Page 9 of 9

APPENDIX B: Instruments of Traceability

Specimen: ArtFelt™ 9mm Acoustic Panel (See Full Report)

<u>Description</u>	<u>Model</u>	<u>Serial Number</u>	<u>Date of Certification</u>	<u>Calibration Due</u>
System 1	Type 3160-A-042	3160-106968	2022-07-12	2023-07-12
Bruel & Kjaer Mic And Preamp C	Type 4943-B-001	2311439	2022-05-02	2023-05-02
Bruel & Kjaer Pistonphone	Type 4228	2781248	2022-07-22	2023-07-22
EXTECH Hygro 959	SD700	A099959	2022-03-22	2023-03-22

APPENDIX C: Revisions to Original Test Report

Specimen: ArtFelt™ 9mm Acoustic Panel (See Full Report)

<u>Date</u>	<u>Revision</u>
2022-11-09	Original report issued

END